

Study the Response of Bubbled Wide Reinforced Concrete Beams with Different Shear Steel Plate Spacing

Amer M. Ibrahim¹, Mohammed J. Hamood², Ahmed A. Mansor³

¹professor, ³Lecturer, Department of Civil Engineering, Engineering College, University of Daiyla,

²Assistant professor, Department of Building & Construction Engineering, University of Technology

aamansor2003@yahoo.com

Abstract

This paper presents an experimental investigation on the behavior of bubbled wide reinforced concrete beams with different shear steel plate spacing. Four specimens with the dimensions of 215x560x1800mm are investigated. The variables studied in this work is using the 10mm stirrups with 125mm spacing and 3mm thickness steel plate with spacing 125, 166 and 250mm instead of reinforcing stirrups. Shear steel plates is good alternative for replacing the stirrups and gives increasing in yield and ultimate loads with 17% and 18% respectively and decreasing the deflection by 8% at yield and 12% at ultimate. Moreover decrease the strain in longitudinal reinforcement by 8% at yield and 24% at ultimate, and reduced the total weight by 2.7%. By increasing the spacing of shear steel plate by 33% and 100%, the results showed that the yield load reduced to 3% and 4% respectively, but the deflection was increased with 37% and 20% (at yield). The strain in interior legs is more than the strain in exterior legs by 189%, 142% and 52% at yield for spacing 125, 166 and 250mm respectively. ACI 318-14 [1] and EC 2 [2] codes give a predicted deflection more than the experimental deflection by 26% and 30% on average respectively.

Keywords: Reinforced Concrete; Wide Beams Stirrups; Shear Steel Plate; Bubbles; Spacing.

Paper History: Received: (14/2/2016), Accepted: (5/4/2016)

1. Introduction

The use of wide concrete beams in structural framing systems has improved in latest years. This is an alteration responds to the necessity for inexpensive keys which reduce structural high and building complexities. For example, engineers of new high-rise buildings are frequently tasked with conveying column loads from the tower portion above required column-free spaces in the pedestal or parking areas below. Wide beams may provide suitable cross-sectional areas to do the required ability

in a shallower depth than a system of slenderer beams at a parallel spacing in the plan.

Adam S. Lubell, et. al [3], carried out an experimental study to investigate the shear behaviour of the wide beams and thick slabs as well as the influence of member width. In their study they tested five specimens of normal strength concrete with a nominal thickness of 470 mm and varied in width from 250 to 3005 mm with 2900mm length. The study demonstrated that the failure shear stresses of narrow beams, wide beams, and slabs are all very similar.

Adam S. Lubell, et. al [4], investigated the influence of the shear reinforcement spacing on the one-way shear capacity of wide reinforced concrete members. A series of 13 normal strength concrete specimens were designed and tested. Shear reinforcement spacing was a primary test variable. The specimens contained shear reinforcement ratios close to (ACI 318-11) minimum requirements [5]. It was concluded that the effectiveness of the shear reinforcement decreases as the spacing of web reinforcement legs across the width of a member increases, the use of few shear reinforcement legs, even when widely spaced up to a distance of approximately 2d, has been shown to decrease the brittleness of the failure mode compared with a geometrically similar member without web reinforcement. To ensure that the shear capacity of all members with shear reinforcement are adequate when designed according to ACI 318-11, the study recommended that the transverse spacing of web reinforcement should be limited to the lesser of both the effective member depth and 600 mm.

Mohamed M. Hanafy [6], investigated the contribution of web shear reinforcement to shear strength of wide beams and the test results clearly demonstrate the significance of the web reinforcement in improving the shear capacity the ductility of the wide beams which is consistent with the recognized international codes and standards provisions.

Amer M. Ibrahim [7], investigates the effect of steel plates on shear strength of wide reinforced concrete beams. All beams have the same dimensions, length of (1800) mm, a width of (560) mm, height of (215) mm and same flexural reinforcement with steel ratio of 0.0025. They are designed to fail in shear. The study shows that the contribution of vertical steel plates to the shear capacity was significant and directly proportional to the existence and direction of the steel plates. The increase in the shear capacity ranged from 9.52% to 47.62% for the range of the tested beams compared with the control beam.

2. The Significance of the Reaserch

The study focuses on behavior of bubbled wide reinforced concrete beams using shear steel plate with different spacing. This technic treats the crowd of stirrups in wide concrete beam because the shear component provided by concrete is very small compared with high depth concrete beams. Also this study is an attempt to reduce the weight of concrete wide beam and study the effect that to: deflection, strain and crack patterns. This system consists of hollow plastic spheres cast into concrete to create a grid of void formers inside the wide beam. Indeed no design code of practice has specified design recommendation for such system.

3. Details of the Exprimental Tests


Out line of Program

The experimental program consisted of four beams with nominal compressive strength of $f'_c = 33\text{MPa}$ (Self Compacting Concrete SCC) and each tested in a four-point loading arrangement. All beams were constructed in the laboratory of the Engineering College of Diyala University. All beams were 560 mm


wide, 215 mm deep, 1800mm long and were tested at a shear span of 600 mm. This gives a shear span-depth ratio (a/d) equal to 3.56. The longitudinal steel reinforcement ratio was $\rho = 2.1\%$, with 16mm diameter and using 10mm diameter in compression reinforcement with 415MPa and 397MPa yield strength respectively.

All the specimens were reinforced with identical longitudinal steel bars. The specimens consist of four wide beams one reference with shear steel reinforcing (stirrups) (WBBS), and three with shear steel plate have equivalent cross sectional area for stirrups at mid legs height and having circular opening 3mm thickness. The spacing between stirrups is 125 mm and it was (125, 166 and 250mm) for shear steel plate (WBPP3-1, WBPP3-2 and WBPP3-3) and the yield strength of shear steel plate is 210MPa. The bubbles are divided into two main groups one in the left side of left concentrated load and the other in the right side of second concentrated load. Every group consists of three rows and the row contains five bubbles. The clear distance between the every bubble in long direction 40mm for stirrups specimen WBBS but it was 40mm, 78mm, and 48mm for WBPP3-1, WBPP3-2 and WBPP3-3 respectively, and the clear distance in transfer direction is 21mm for all specimens. The different spacing of bubbles in long direction was setting as a result of the different spacing of shear steel plate.

Typical concrete dimensions and reinforcement details of the tested specimens are illustrated in Figure 1. The placements of bubbles, longitudinal reinforcement, shear steel plate and mold specimen are shown in Figure 2.

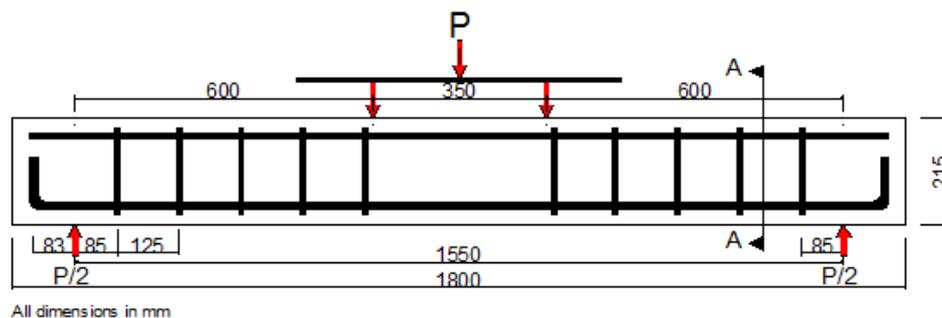

A- Loading details

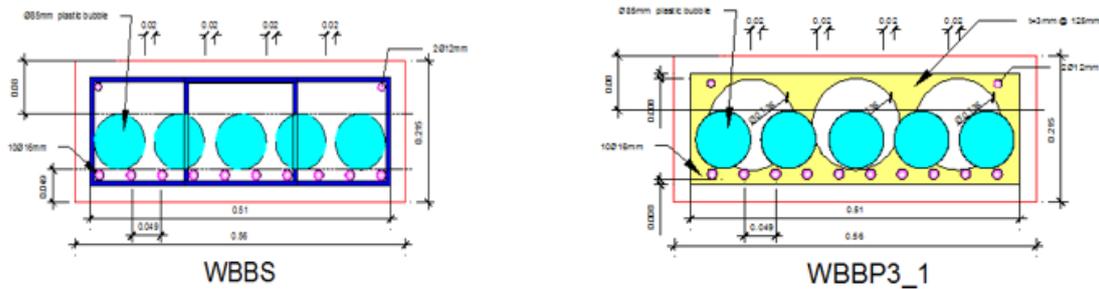

B- Section A-A for stirrups

C- Section A-A for plates

Figure 1 A-Loading details, B-Section A-A for stirrups, C-Section A-A for plates



Figure 2: Preparation the mold specimen and placing the reinforcement

Tested Method and Measurements

All beams were tested under simply supported condition over a span 1.8m with their tension faces uppermost as shown in Figure 1 For all beams, the first crack load, deflection under loading point, steel plate strains, yield and ultimate load were measured.

4. Test Results

The strength characteristics of all specimens (f_c , yield ultimate load and deflection, at yield and ultimate loads also the values of ductility) were tabulated in Table 1. Great care was taken in marking the load at which the first crack formed. The experimental values of the cracking loads were obtained from load-deflection diagrams.

4.1 Load Deflection Relationships

Table 1 shows the values of deflection at yield and ultimate load that were obtained from load-deflection diagrams. It can be seen from Table 1 that the deflection at yield was increased in specimens that used the shear steel

plate with 17%, 14% and 14% for specimens WBBP3-1, WBBP3-2 and WBBP3-3 respectively; this is obvious, due to the regular gradation increasing of yielding load. This increasing of deflection was clear in ultimate load for the specimens WBBP3-2 and WBBP3-3 when it compared with the WBSB specimen by 39% and 11% respectively but it decrease by 12% for WBBP3-1. For the three specimens WBBP3-1, WBBP3-2 and WBBP3-3, it can be seen from Table 1 that by increasing the spacing of shears steel plate by 33% and 100%, that the deflection at yield was increased with 37% and 20% respectively this is obvious, due to increasing of shear steel plate spacing. This increasing of deflection was clear at ultimate load for the specimens WBBP3-2 and WBBP3-3 when comparing with the WBBP3-1 specimen by 59% and 27% respectively, as a result of increasing of spacing of shear steel plate. Figure 3 shows the load- deflection curves for the specimens. It can be seen that the deflection at yield were close between all specimens, but the behaviour is different at ultimate load corresponding to decrease of ultimate load. Also it can be seen that the WBBP3-2 specimen is more ductile compared with the other specimens.

Table 1 Strength characteristics of tested specimens

Beam Specimens	P_y kN	% diff. of Yield load	P_u kN	% diff. of Ult. load	Δ_y Mm	% diff. of Δ_y	Δ_u mm	% diff. of Δ_u	Ductility $\frac{\Delta_u}{\Delta_y}$	Weight (ton)	% diff. of Weight	Failure
WBBS	361	---	378	---	13.40	---	25.70	---	1.92	0.499	---	Flex.
WBBP3-1	421	17%	446	18%	12.30	-8%	22.50	-12%	1.83	0.486	-2.3%	Flex.
WBBP3-2	410	14%	430	14%	16.85	26%	35.75	39%	2.12	0.484	-2.7%	Flex.
WBBP3-3	410	14%	431	14%	14.80	10%	28.60	11%	1.93	0.482	-3.1%	Shear

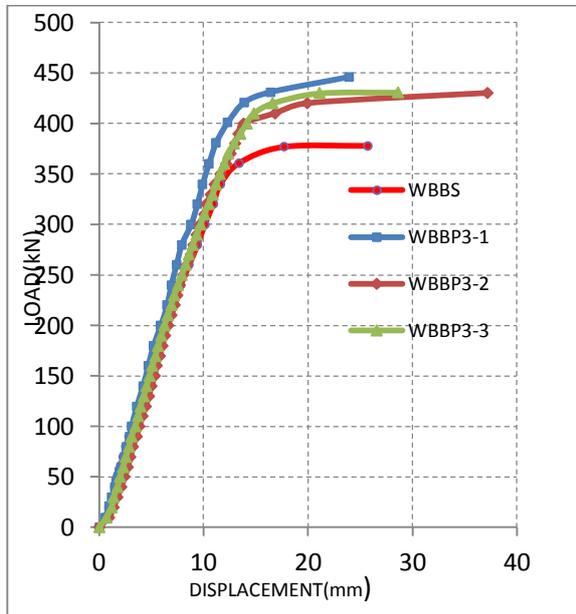


Figure 3: Load-deflection curves of specimens

4.2 Comparison the Deflection Predicted by ACI 318-14 [1] and EC 2 [2] codes

Table 2 shows the values of deflection at service load (assume 60% from the ultimate load) obtained from load-deflection diagrams, also the analytical results of all specimens computing by ACI 318-14 [1] and EC 2 [2] codes at service load were presented in Table 2, it can be seen that, the predicted deflection of wide beams calculated by ACI 318-14 [1] (as per to equation 1) and EC 2 [2] (as per to Equations 2,3,4,5, and 6) codes computed by Equation 1 and 2) were less than the experimental deflection by 26% and 30% on average respectively.

$$\Delta_{max} = \left(\frac{P \cdot a(3L^2 - 4a^2)}{48E_c I_{effective}} \right) \quad (1)$$

$$\xi = 1 - 0.5 \left(\frac{M_{cr}}{M_a} \right)^2 \quad (2)$$

$$\frac{1}{r_n} = \xi \left(\frac{M_{QP}}{EI_c} \right) + (1 - \xi) \left(\frac{M_{QP}}{EI_u} \right) \quad (3)$$

$$\frac{1}{r_{i,QP}} = \left(\frac{1}{r_n} \right) + \left(\frac{1}{r_{cs}} \right) \dots \text{ (i.e } \Phi) \quad (4)$$

$$\delta_{QP} = kl^2 \frac{1}{r_{i,QP}} \quad (5)$$

$$K_i = \left(0.125 - \frac{(a/l)^2}{6} \right) \quad (6)$$

It can be explained this increasing in experimental deflection because the dial gauge was recorded the deflection in center of wide beams in longitude and transferred directions and not consider the deflections at edges for centre of beam. This case attributed to Saint-Venant's principle. Saint-Venant's states that in a body under the action of a system of forces which are applied in a limited region of its boundary, the stresses and strains induced by those forces in another region of the body, located at a large distance from the region where the forces are applied, do not depend on the particular way the forces are applied, but only on their resultant. This large distance may be considered, in most cases, as the largest dimension of the region where the forces are applied [8]. From the other hand, the predicted

deflection of wide beams as per ACI 318-14 [1] and EC 2 [2] codes, take all cross section of

concrete without any subtract of volume of concrete displaced by hollow bubbles.

Table 2 Experimental deflection comparing with deflection computing by of ACI 318-14 [1] and EC 2 [2] cods at service load

Beam Specimens	Deflection at Service Load, Δ_s (mm)				
	Measured (mm)	Predicted			
		ACI 318M-14		EC 2	
			%Difference		%Difference
WBBS	3.6	2.60	-27.64	2.51	-30.27
WBBP3-1	3.7	3.07	-16.81	2.90	-21.62
WBBP3-2	4.5	3.00	-33.27	2.81	-37.55
WBBP3-3	4.1	3.00	-26.70	2.86	-30.24

4.3 Strain Characteristics in Longitudinal Reinforcement and Compression Face of Concrete

Table 3 shows the values of strain in middle of longitudinal reinforcement bar and on parallel place of concrete face (in compression) at crack, yield and ultimate load that were obtained from strain gauge connected to data logger.

Table 3 Strain characteristics in longitudinal reinforcement and concrete of specimens

Beam Specimens	Longitudinal Reinforcement				Concrete (Compression)			
	ϵ_y x10 ⁻³	% diff. of ϵ_y	ϵ_u x10 ⁻³	% diff. of ϵ_u	ϵ_y x10 ⁻³	% diff. of ϵ_y	ϵ_u x10 ⁻³	% diff. of ϵ_u
WBBS	2.97	---	4.78	---	-1.59	---	-2.94	---
WBBP3-1	2.67	-10%	3.61	-24%	-1.92	21%	-2.95	0.3%
WBB3-2	2.47	-17%	2.80	-41%	-2.43	53%	-4.00	36%
WBBP3-3	2.16	-27%	3.02	-37%	-1.84	16%	-2.84	-3.4%

4.3.1- Strain in Longitudinal Reinforcement

It can be seen from Table 2 that the strain in longitudinal reinforcing at yield and ultimate loads, is regular gradation decreasing in specimens WBBP3-1, WBBP3-2 and WBBP3-3 that used the shear steel plate with 10%, 17% and 27% (at yield) and by 24%, 41% and 37% (at ultimate) respectively with respect to control beam WBBS. By increasing the spacing of shear steel plate by 33% and 100%, it can be seen from Table 2 that the strain in

longitudinal reinforcement at yield and ultimate loads is decreased by 7.7% and 19% (at yield), and by 22% and 16% (at ultimate) for the specimens WBBP3-2 and WBBP3-3 respectively compared with WBBP3-1 specimen, the decreasing in strain at yield and ultimate loads may be as a result of decreasing of yield and ultimate loads of WBBP3-2 and WBBP3-3.

4.3.2- Strain in Compression Face of Concrete

Based on Table 2, the strain in compression face of concrete (at middle top face of specimens) is increased for the specimen WBBP3-1 WBP3-2 and WBP3-3 compared with WBBS at yield load by 21%, 53% and 16%. By increase the spacing of shear steel plate by 33% and 100%, the strain in compression face of concrete (at middle top

face of specimens) is increased at yield and ultimate loads by 27% and 35% respectively for the specimens WBBP3-2 compared with WBBP3-1 specimen but it decreased by 4.4% and 3.7% respectively for WBBP3-3. The strain profile of four specimens is shown in Figure 4, 5, 6 and 7.

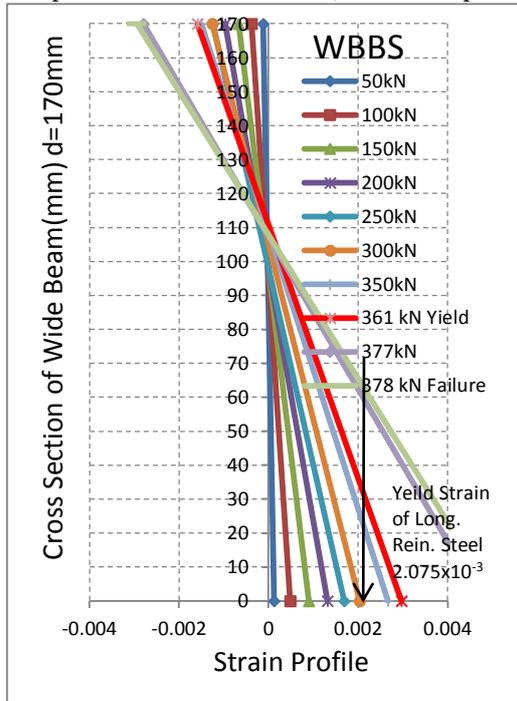


Figure 4: Strain profile of WBBS specimen

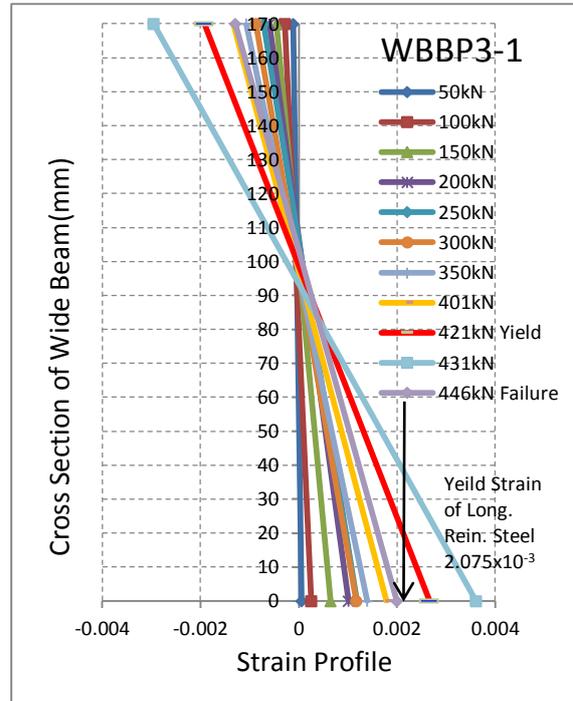


Figure 5: Strain profile of WBBP3-1 specimen

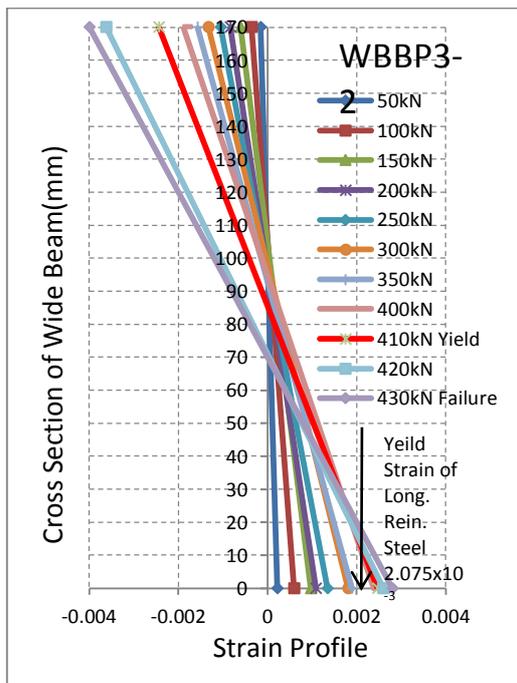


Figure 6: Strain profile of WBBP3-2 specimen

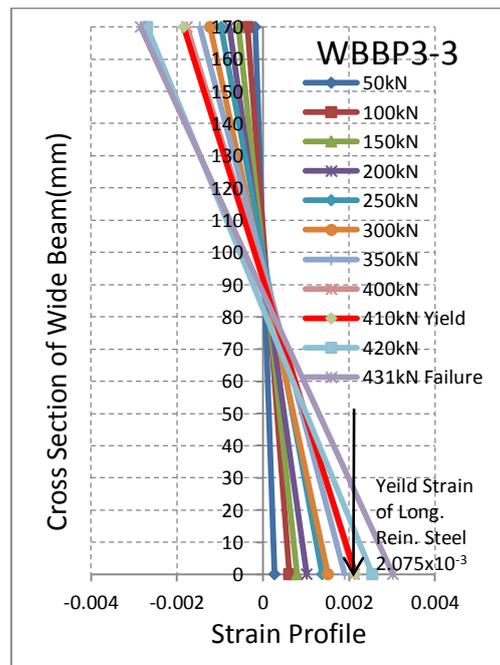


Figure (7): Strain profile of WBBP3-3 specimen

4.4 Strain Characteristics in Exterior and Interior Legs of Shear Steel Plate

Table 3 shows the values of strain in exterior and interior legs of shear steel plate at yield and ultimate load that were obtained from strain gauge connected to data logger.

4.4.1- Strain in Exterior Leg of Shear Steel Plate

It can be seen from Table 4 that the strain exterior leg of shear steel plate is decreased by 28% and 6% for WBBP3-1 and WBBP3-2 respectively in comparison with WBBS at yield load, but it was increase by 383% for WBBP3-3. At ultimate load it is decreased by 17% and 5% for the specimens WBBP3-1 and WBBP3-2, but it was increased by 517% for WBBP3-3 as a result of sudden shear failure. By increasing the spacing of shear steel plate by 33% and 100%, it can be seen that the stain in specimens WBBP3-2 and WBBP3-3 is more than strain of WBBP3-1 by 35%, and 573% respectively (at yield) and by 14% and 643% respectively (at ultimate). This increasing in strain exterior leg of shear steel plate at yield and ultimate load stages may be due to decreasing the number of shear steel plate and increasing of spacing and decreasing of concrete shear component as a result of the presence of bubbles.

4.4.2- Strain in Interior Leg of Shear Steel Plate

It can be seen from Table 4 that the strain of interior leg of shear steel plate is increased by 47%, 61% and 418% for WBBP3-1, WBBP3-2 and WBBP3-3 respectively in comparison with WBBS at yield load, and by 84%, 133% and 474% at ultimate load. The high increasing in interior leg strain for WBBP3-3 specimen is a result of sudden shear failure. By increasing the spacing of shear steel plate by 33% and 100%, it can be seen that the stain in specimens WBBP3-2 and WBBP3-3 is more than strain of WBBP3-1 by 10%, and 253% respectively (in yield) and by 26% and 213% respectively (in ultimate). This increasing in strain interior leg of shear steel plate at yield and ultimate load stage may be due to decreasing the number of shear steel plate and increasing of spacing and decreasing of concrete shear component as a result of bubbles present. The main notice was observed that the difference between the stain in exterior and interior legs. It is clear that the strain in interior leg is more than strain in exterior leg about 41%, 189%, 142% and 52% for WBBS, WBBP3-1, WBBP3-2 and WBBP3-3 respectively at yield load, and about 35%, 199%, 231% and 25% respectively at ultimate load.

Table 4 Strain characteristics in shear steel plate (Exterior and Interior legs) of specimens

Beam Specimens	Shear Reinforcement or Steel Plate(exterior leg)				Shear Reinforcement or Steel Plate(interior leg)			
	ϵ_y x10 ⁻³	% diff. of ϵ_y	ϵ_u x10 ⁻³	% diff. of ϵ_u	ϵ_y x10 ⁻³	% diff. of ϵ_y	ϵ_u x10 ⁻³	% diff. of ϵ_u
WBBS	0.752	---	0.853	---	1.06	---	1.15	---
WBBP3-1	0.539	-28%	0.709	-17%	1.56	47%	2.12	84%
WBBP3-2	0.706	-6%	0.810	-5%	1.71	61%	2.68	133%
WBBP3-3	3.630	383%	5.270	517%	5.50	418%	6.60	474%

4.5- Comparison between the Yield and Ultimate Strain (Nominal and Experimental) of Steel Plate

Table 5 explains a comparison of the yield and ultimate nominal strain and experimental strain in shear reinforcement (stirrups) and shear steel plate for interior leg. It can be seen that:

1. In all specimens the experimental strain at yield and ultimate it is reached to the nominal yield and ultimate strain of stirrups or plate except WBBS specimen (at yield).
2. The experimental strain at yield load is less than nominal strain by 57% for the specimen WBBS while the experimental strain at yield load and it is more than nominal strain by 48% 63% and 524% for

the specimen WBBP3-1, WBBP3-2 and WBBP3-3 respectively.

- The experimental strain at ultimate load is more than nominal strain by 70% for the specimen WBBS while the experimental strain at ultimate is more than nominal strain by 41% 78% and 440% for the specimen WBBP3-1, WBBP3-2 and WBBP3-3 respectively.

4.6- Crack Pattern

The tested beams at different stages of loading are shown in details in Figure 8 and Plate 1. The bearing numbers inside the circles represent the sequence of formation of the cracks, while the numbers shown under the beams between those representing the sequence are the cracks spacing. The sign (*) represents to the first crack width appeared.

From these figures the following conclusions can be drawn:

- Due to the constant moment applied within the middle third of the beam the sequence of formation of cracking was random, and cracks grew upward with the increase of the applied load.

- Cracks forming within the middle third of the beams were generally vertical due to the pure moment applied on this part of the beam. Outside this zone the cracks became inclined due to the presence of shearing forces in addition to the moment.



The specimen WBP3-3 was failed under high shear action. When the diagonal crack occurs, there must be a redistribution of internal forces at the cracked section. And when the beam has no web reinforcement, the external shear resisted by the concrete web must be redistributed partly to the tensile reinforcement through dowel action but mainly to the compression zone of concrete. The redistribution must take place by the web reinforcement. For the WBBP3-3 the failure was immediately happen, it is possible interpreted that the member does not accept any redistribution when the diagonal crack forms. In this case, the web reinforcement will yield immediately and the compression zone will be destroyed immediately [9]. The main difference between crack pattern of bubbled specimens is related to the shape of shear cracks. The shear cracks are tack the inclined and take a polyline around the bubbles.

Table 5 Strain characteristics in shear steel interior plate leg

Specimens	f_y (MPa)	f_u (MPa)	ϵ_y $\times 10^{-3}$	ϵ_y $\times 10^{-3}$ Experimental	$\frac{\epsilon_y \text{ exp.}}{\epsilon_y}$	ϵ_u $\times 10^{-3}$	ϵ_u $\times 10^{-3}$ Experimental	$\frac{\epsilon_u \text{ exp.}}{\epsilon_u}$
WBBS	397	685	1.985	1.06	0.53	1.15	1.96	1.70
WBBP3-1	210	300	1.050	1.56	1.48	1.50	2.12	1.41
WBBP3-2	210	300	1.050	1.71	1.63	1.50	2.68	1.78
WBBP3-3	210	300	1.050	5.50	5.24	1.50	6.60	4.40

Table 6 First crack width, number and spacing of shear cracks for specimens

Beam Specimens	1 st Crack at Cracking		1 st Crack at Yield		No. of Cracks		Spacing of Shear Cracks(mm)		
	Load (kN)	Width (mm)	Load (kN)	Width (mm)	flexural	Shear	Min. Spacing	Max. Spacing	Average Spacing
WBBS	40	0.005	361	0.20	6	11	50	100	75
WBBP3-1	60	0.005	421	0.26	4	9	50	140	100
WBBP3-2	50	0.005	410	0.20	5	10	40	160	95
WBBP3-3	40	0.005	410	0.18	5	11	50	140	122

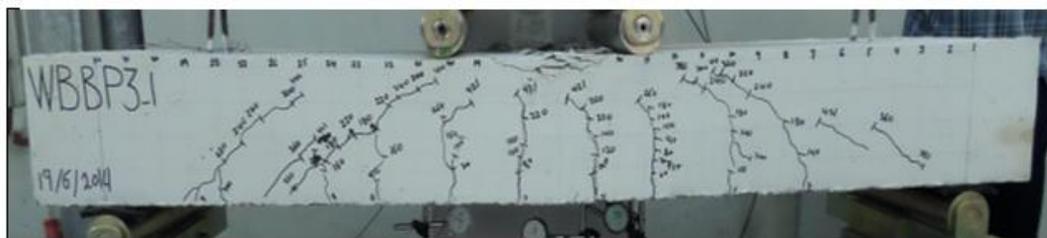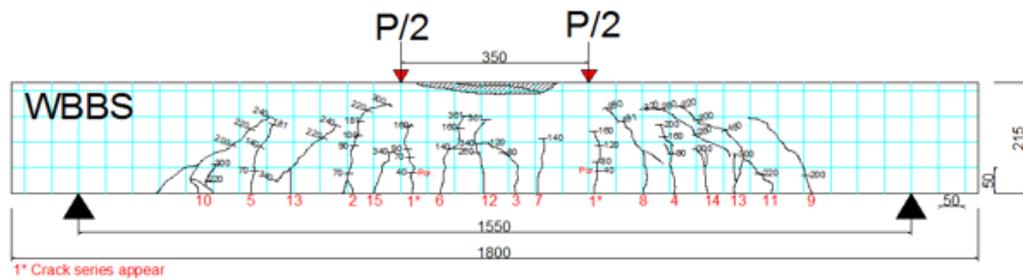

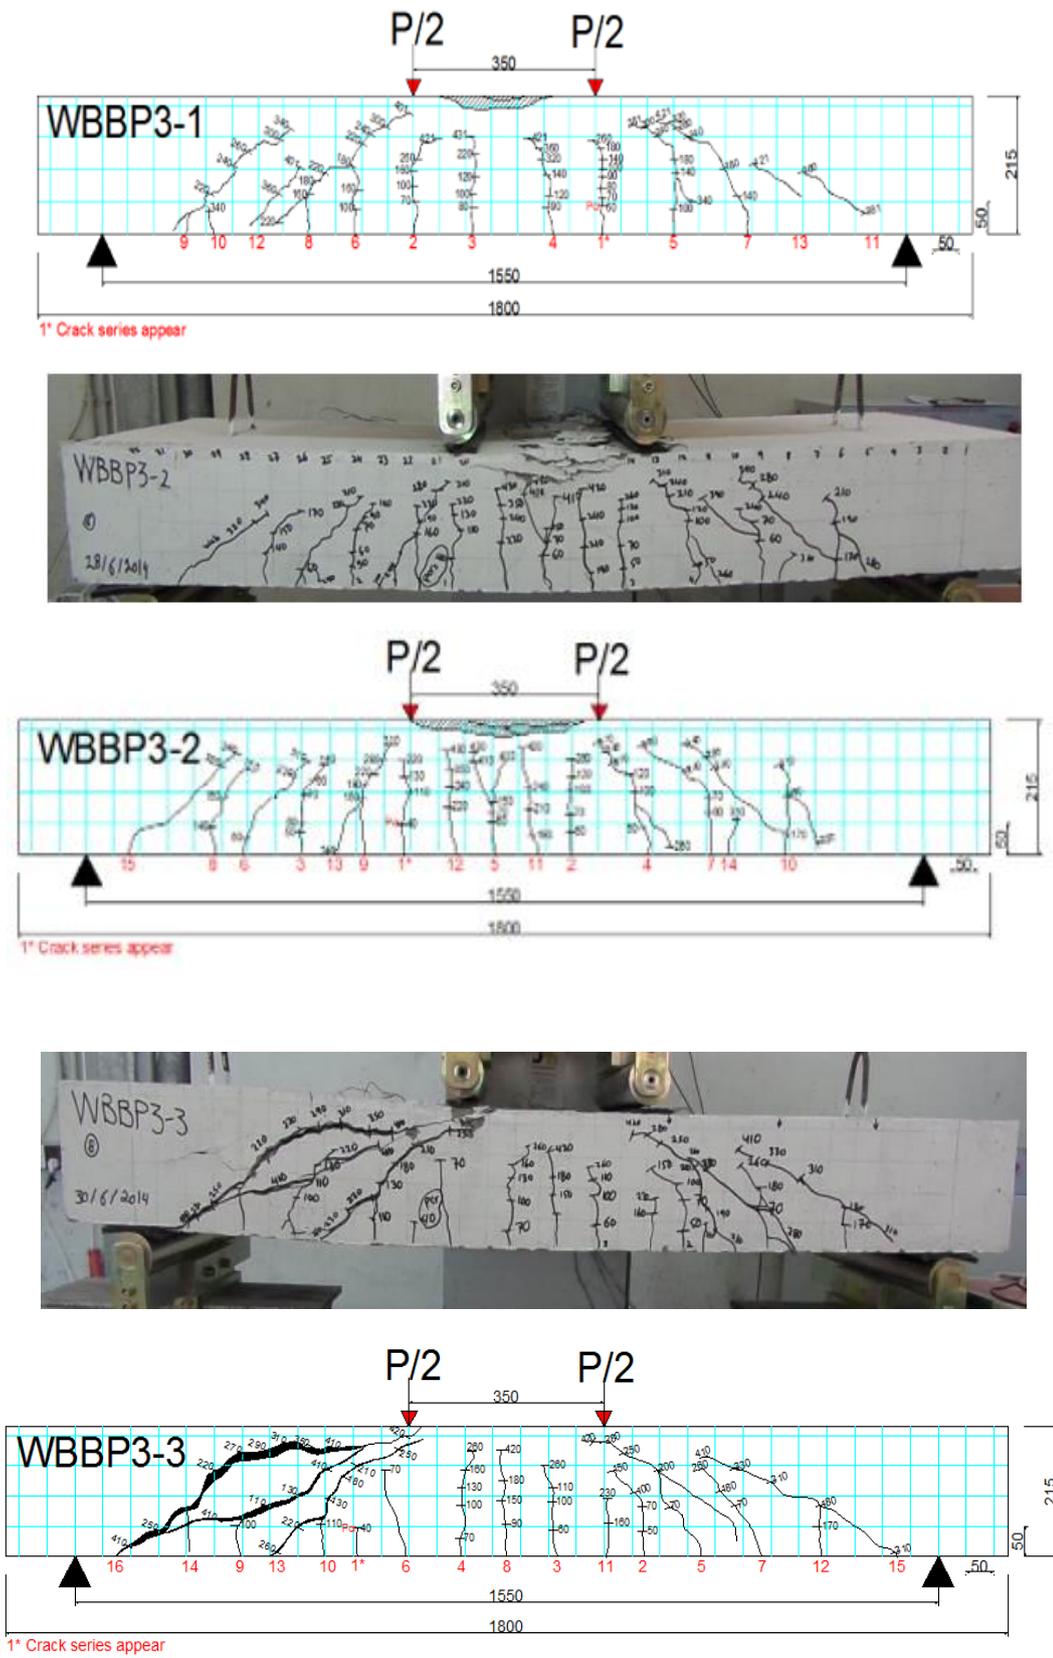


Plate 1 and Figure 8

4.7- The First Crack Width

It can be seen from Table 6, the crack width of the first crack at cracking and yield load. The first crack appeared randomly within the middle third of the span (zone of maximum moment), was not necessarily the widest one. The first crack width at cracking load is equally in all specimens as a result of the same properties of concrete and longitudinal reinforcing. Also the first crack width at yield load is close in specimens except increasing by 30% for WBBP3-1 compare with WBBS specimen as a result of increasing the yield load.

0.12mm and 0.21mm on average. The predicted crack width at service and yield loads of wide beams computing by ACI 318M-14 [1] and EC 2 [2] codes (0.21 and 0.33) mm and (0.12 and 0.19) mm on average respectively. So it can be seen that:

1. The experimental crack width at service and yield load was more than predicted crack width computed by ACI 318M-14 [1] by 68% and 56% respectively.
2. The experimental crack width at service was close to predicted crack width computed by EC 2 [2] but it was less than the experimental crack width by 11% at yield load.

Table 7 First crack width, number and spacing of shear cracks for specimens

Beam Specimens	Crack Width (mm)					
	Experimental		According ACI 318M-14		According EC 2	
	At Service load	At Yield load	At Service load	At Yield load	At Service load	At Yield load
WBBS	0.11	0.20	0.188	0.327	0.109	0.190
WBBP3-1	0.16	0.26	0.221	0.327	0.128	0.190
WBBP3-2	0.12	0.20	0.215	0.327	0.125	0.190
WBBP3-3	0.12	0.18	0.215	0.327	0.125	0.190

4.8- Shear Cracks Spacing

Concerning the number of shear cracks, it can be seen from Table 6 that the number of shear cracks was close except decreasing by 18% for WBBP3-1 compare with WBBS specimen. Minimum spacing of shear cracks was close in specimens with 50mm, but the maximum and average spacing was increased by 40%, 60% and 40% (maximum) and by 33%, 26% and 63% (average) for WBBP3-1, WBBP3-2 and WBBP3-3 compare with WBBS. By increasing the spacing of shear steel plate by 33%, 100%, the number of shear cracks was increased by 11% and 22% respectively.

4.9- Comparison the First Crack width Computing by ACI 318M-14 [1] and EC 2 [2] Codes

It can be seen from Table 6, the experimental crack width of the first crack at service and yield load comparing with predicted first crack width according to the ACI 318M-14 [1] and EC 2 [2] codes. The experimental crack width of all specimens at service and yield load was

3. From (1) and (2) above EC 2 [2] code was more conservative than ACI 318M-14 [1].

4.10- Comparison the Crack Spacing Computing by ACI 318M-14 [1] and EC 2 [2] Codes

Table 8 shows the measured and predicted values of crack spacing according to BS8110-85 [10] and EC 2 [2] only because no such formulas were proposed in other codes of design [1]. In BS8110-85[10], the average crack spacing approximately equal $1.67(h-x)$ for primary cracks, in this method the height of neutral axis determines the spacing of cracks. It can be seen from Table 8 that:

- (1) The predicted mean crack spacing according to BS8110-85 [10] ranged between 215mm and 220mm for all four wide beams tested. And the experimental average crack spacing ranged 76mm to 105 mm. By comparing the values obtained experimentally and those predicted using BS8110-85 [10] formula, it can be seen that the predicted values more than experimental values by 140% on average.

(2) The predicted minimum and maximum crack spacing according to EC 2 [2], 92mm and 160mm respectively all four wide beams tested. From Table 7 it can be seen that the EC 2 [2] formula did not consider the concrete compressive strength, thus for all the investigated specimens, the crack spacing were the same for beams with the identical reinforcement. This was noted that situation obtained experimentally; the minimum and maximum crack spacing was bounded by (40mm to 50mm), and by (120mm and 160mm) respectively. By comparing the values obtained experimentally and those predicted using EC 2⁽²⁾ formula, it can be seen that it can be seen that the predicted values of minimum and maximum spacing is more than experimental values by 104% and 12% on average.

A modification in the formulas proposed by BS8110-85 [10] and EC 2 [2] are needed to consider the spacing of shear reinforcement.

4.11- Comparison between the Weights of Specimens

It can be seen from Table 1 that using the shear steel plate was reduced the weight by 2.3%, 2.7% and 3.1% for specimens WBBP3-1, WBBP3-2 and WBBP3-3. It is clear that using shear steel plate is reduced the weight of specimens by 2.7%. But the weight was

Table 8 Comparing of number of cracks and experimental crack spacing with crack spacing computing by of BS 8110⁽¹⁰⁾ and EC 2⁽²⁾ cods

Beam Specimens	No. of Cracks		Spacing of Cracks (mm)					
			Experimental			According BS 8110	According EC 2	
	flexural	Shear	Min. Spacing	Max. Spacing	Average Spacing	Mean Spacing	Min. Spacing	Max. Spacing
WBBS	6	11	40	120	76	219	91.8	160
WBBP3-1	4	9	50	150	105	220	91.8	160
WBBP3-2	5	10	40	160	93	215	91.8	160
WBBP3-3	5	11	50	140	93	216	91.8	160

displaced by bubbles was around 4.7% from the total weight of sold beam (without bubbles).

5. Conclusions and Recommendations

1. Shear steel plate is a good alternative for replacing stirrups (as web reinforcement) in bubbled wide beams and gives increasing at yield and ultimate load with 17% and 18% of yield and ultimate load respectively.
2. Replacing stirrups by shear steel plate in bubbled wide beams gives a reduction in deflection at yield and ultimate load with 8% and 12% of yield and ultimate load respectively.
3. Replacing stirrups by shear steel plate in bubbled wide beams decrease the strain in longitudinal reinforcement by 10% and 24% of yield and ultimate load respectively.
4. Using shear steel plate, reduce the stain in exterior leg by 28% compared with stirrups, although the yield strength of shear steel plate is less than stirrups yield strength by 47%.
5. Using the shear steel plate instead of stirrups reduced the total weight of wide beams by 2.7%. Also using the bubbles in specimens was displaced 4.7% from the total weight of specimen.
6. By using steel shear plate of 3mm thickness, with spacing between steel

plates of 125, 166 and 250 mm (increasing the spacing by 33% and 100%), and it can be notified:

- The deflection at yield was increased by 37% and 20% respectively.

- The yield and ultimate loads are reduced by 3% and 4% respectively.
 - The strain in longitudinal reinforcing was decreased by 7.7% at yield and by 22% and 16% respectively at ultimate load.
 - The strain in exterior leg was increased by 35% and 573% respectively at yield load and by 14% and 643% respectively for the interior legs.
 - At yield: the strain in interior legs is more than the strain in exterior leg by 189%, 142% and 52%.
 - The number of shear cracks is increased by 11% and 22% respectively.
7. The predicted deflection of wide bubbled beams as per ACI 318-14 [1] and EC 2 [2] codes were less than the experimental deflection by 26% and 30% on average respectively.
 8. EC 2 [2] code was more conservative than ACI 318M-14⁽¹⁾ to predicted the crack width.
 9. A modification in the formulas proposed by BS8110-85 [10] and EC 2 [2] are needed to consider the spacing of shear cracks.

References:

- [1] ACI Committee 318M-14, Building Code Requirements for Structural Concrete and Commentary, American Concrete Institute, Farmington Hills, MI, (2014), pp 465.
- [2] Eurocode 2, Design of Concrete Structures—Part 1-1: General Rules and Rules for Buildings (EN1992-1-1), European Committee for Standardization, Brussels, Belgium, Dec. (2004), pp225.
- [3] Adam S. Lubell, Edward G. Sherwood, Evan C. Bentz, and Michael P. Collins (2006), One way shear strength of thick slabs and wide beams, ACI Structural Journal, Vol. 103, no. 6, Nov. - Dec. 2006, pp. 794-802.
- [4] Adam S. Lubell, Evan C. Bentz, and Michael P. Collins (2009), Shear reinforcement spacing in wide members, ACI Structural Journal, vol. 106, no. 2, March - April 2009, pp. 205-214.
- [5] ACI Committee 318 (2011): Building code requirements for structural concrete (ACI 318-11) and commentary (318R-11). Farmington Hills: American Concrete Institute.
- [6] Mohamed M. Hanafy, Hatem M. Mohamed and Nabil A.B. Yehia (2012), On the Contribution of Shear Reinforcement in Shear Strength of Shallow Wide Beams, Life Science Journal Vol. 9, no. 3, 2012, pp. 484-498.
- [7] Amer M. Ibrahim, Wissam D. Salman, Qusay W. Ahmed, (2015), Effect of steel plates on shear strength of wide reinforced concrete beams, Journal of Engineering and Development, Vol.19, No.3, May. (2015), ISSN 1813- 7822.
- [8] Ferdinand P. Beer E. Russell Johnston, Jr. John T. De Wolf, (2009), Mechanics of Materials, Lecture Notes: J. Walt Oler Texas Tech University.
- [9] ACI-ASCE Committee 326, shear and diagonal Tension
- [10] Structural Use of Concrete –Part 2 Code of Practice for Design and Construction (8110), (1985), British Standard Institution, London.